

CHEMICAL COMPOSITION

| C | Cr | Mo | W | V |
|------|------|------|------|------|
| 2.48 | 4.20 | 3.10 | 4.20 | 8.00 |

STANDARDS

- Europe: HS 4-3-8
- Germany: 1.3352

DELIVERY HARDNESS

| | |
|---------------|-------------|
| Soft annealed | max. 300 HB |
| Cold drawn | max. 340 HB |
| Cold rolled | max. 340 HB |

DESCRIPTION

ASP[®]2053 is a high V-alloyed grade with excellent abrasive wear resistance and toughness.

APPLICATIONS

- Cold work tools
- Wood tools
- Paper cutting knives
- Stamping
- Textile knives
- Fine blanking
- Extrusion
- Rolls

FORM SUPPLIED


- Coils
- Round bars
- Forged blanks
- Flat & square bars
- Sheets
- Discs

Available surface conditions: drawn, ground, peeled, rough machined, hot rolled.

HEAT TREATMENT

- Soft annealing in a protective atmosphere at 850-900°C for 3 hours, followed by slow cooling at 10°C/h down to 700°C, then air cooling.
- Stress-relieving at 600-700°C for approximately 2 hours, slow cooling down to 500°C.
- Hardening in a protective atmosphere at a temperature suitable for chosen working hardness. Pre-heating in 2 or 3 steps depending on tool dimension-design and austenitising temperature, last step 50°C below chosen austenitising temperature. Cooling down to 40-50°C.
- Tempering at 560°C three times for at least 1 hour each time. Cooling to room temperature (25°C) between temperings.

GUIDELINES FOR HARDENING

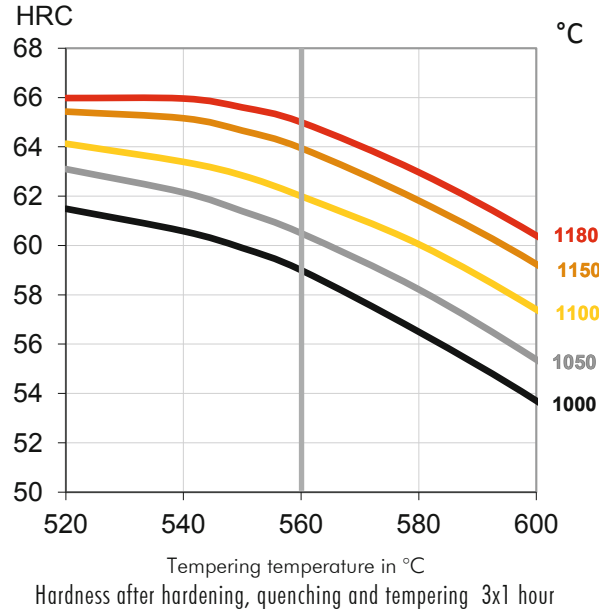

PROCESSING

ASP[®]2053 can be worked as follows :

- Machining (grinding, turning, milling)
- Polishing
- Plastic forming
- Electrical discharge machining
- welding (special procedure including preheating and filler materials of base material composition).

GRINDING

During grinding, local heating of the surface, which may alter the temper, must be avoided. Grinding wheel manufacturers can furnish advice on the choice of grinding wheels.

SURFACE TREATMENT

The steel grade is a good substrate material for PVD and CVD coating. If nitriding is requested a small zone of 2-15 µm is recommended. The steel grade can also be steam-tempered if so desired.




PHYSICAL PROPERTIES

| Temperature | 20°C | 400°C | 600°C |
|--|------|-----------------------|-----------------------|
| Density g /cm ³ (1) | 7.7 | 7.6 | 7.5 |
| Modulus of elasticity kN/mm ² (2) | 250 | 220 | 200 |
| Thermal expansion coefficient from 20°C per °C (2) | - | 12,1x10 ⁻⁶ | 12,7x10 ⁻⁶ |
| Thermal conductivity W/m°C (2) | 24 | 28 | 27 |
| Specific heat J/kg °C (2) | 420 | 510 | 600 |


(1) = Soft annealed

(2) = Hardened 1180°C and tempered 560°C, 3x1 hour

IMPACT ENERGY

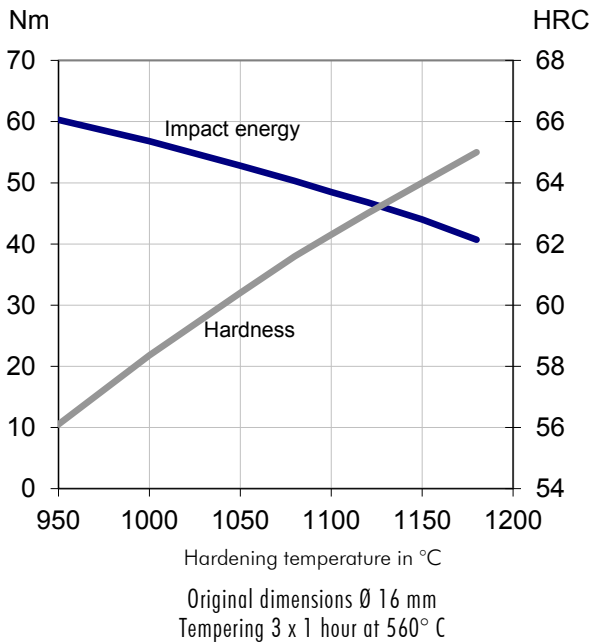


4-POINT BEND STRENGTH

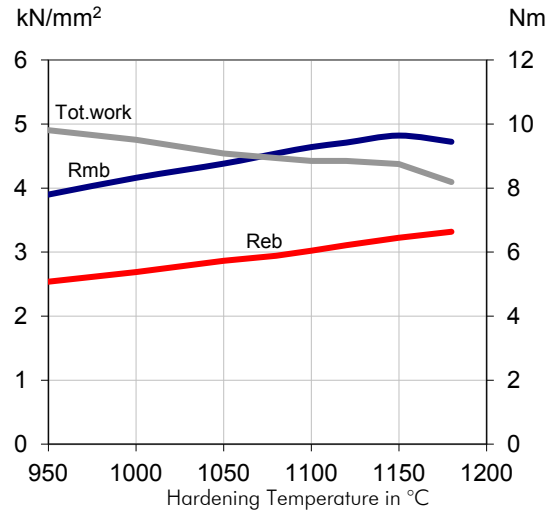


Original dimensions Ø 16 mm
Tempering 3 x 1 hour at 560°C
Dimensions of test piece Ø 4.7 mm

Rmb = Ultimate bend strength in kN/mm²
Reb = Bend yield strength in kN/mm²
Tot. work = Total work in Nm

COMPRESSION YIELD STRESS

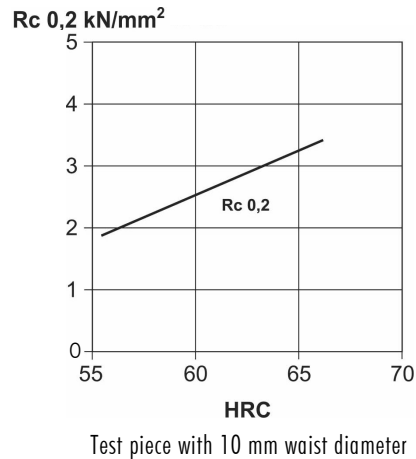

COMPARATIVE PROPERTIES

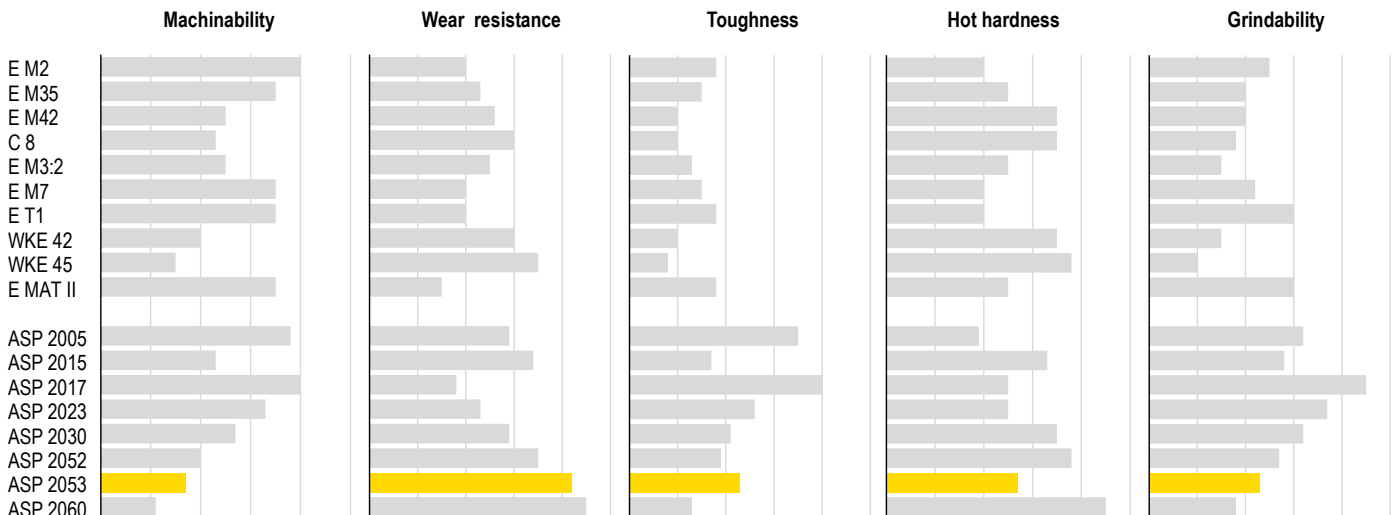

Recommendations for machining in soft annealed condition, 260-300 HB

| TURNING | CEMENTED CARBIDE | | HSS |
|------------------------------|---------------------------|-----------------------|----------|
| | Medium turning | Finishing turning | |
| Cutting speed, v_c (m/min) | 80-110 | 110-130 | 10-15 |
| Feed, f (mm/rev) | 0.2-0.4 | 0.05-0.2 | 0.05-0.3 |
| Cutting depth, a_p (mm) | 2-4 | 0.5-2 | 0.5-3 |
| Tools according to ISO | coated carbide P10-P20 | coated carbide P10 | coated |

Use a wear resistant coated cemented carbide e.g Coromant 4015 or Seco TP 100.
Black ceramics are usually the best tools at finish turning, e.g. Coromant 650 or Feldmühle SH20.

| END MILLING SLOT MILLING | DIAMETER (mm) | DIAMETER (mm) | | | | |
|----------------------------------|------------------------------|--------------------------|-----------|-----------|-----------|-----------|
| | | 3-5 | 5-10 | 10-20 | 20-30 | 30-40 |
| Coated HSS | Cutting speed, v_c (m/min) | 15-20 | 15-20 | 15-20 | 15-20 | 15-20 |
| | Feed, f_z (mm/tooth) | 0.005-0.01 | 0.01-0.02 | 0.02-0.03 | 0.03-0.05 | 0.05-0.07 |
| Coated solid cemented carbide | Cutting speed, v_c (m/min) | 40-45 | 40-45 | 40-45 | - | - |
| | Feed, f_z (mm/tooth) | 0.006-0.01 | 0.01-0.02 | 0.02-0.04 | - | - |
| Indexable carbide tips | Cutting speed, v_c (m/min) | - | - | 80-110 | 80-110 | 80-110 |
| | Feed, f_z (mm/tooth) | - | - | 0.06-0.10 | 0.10-0.12 | 0.15-0.20 |
| Suitable tools | - | coated carbide, K15, P25 | | | | |


SIDE MILLING

The same cutting speed can be used in side milling as in slot milling. However, the feed has to be adjusted to produce an adequate chip thickness.

The diameter of the mill (D) over the radial depth of cut (a_e) is used as a parameter. Read the correction coefficient (C_f) from the diagram and multiply by the feed for slot milling from the table above.


Comments (slot and side milling)


1. Coated tools are always recommended for end milling both with HSS tools and cemented carbide tools. TiCN, TiAlN or multilayer (Futura) is preferred.
2. The cutting speed must be decreased considerably if uncoated tools are used.

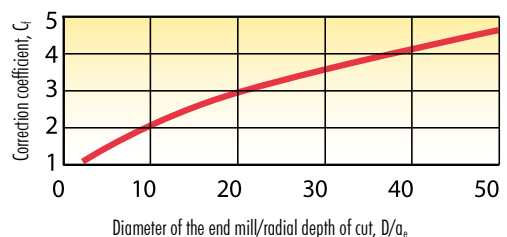


Example

| | |
|--------------------------|-------------------------------------|
| Tool | End mill with indexable tips |
| Diameter of the end mill | D=40 mm |
| Radial depth or cut | $a_e=2$ mm |
| D/ a_e | 40/2=20 |
| Correction coefficient | $C_f=2.8$ |
| Feed | $f_z=2.8 \times 0.17=0.48$ mm/tooth |
| Cutting speed | $v_c=50$ m/min |

| FACE MILLING  | CEMENTED CARBIDE TOOL | |
|--|----------------------------------|---------------------|
| | Rough machining | Finishing machining |
| Cutting speed, v_c (m/min) | 60-90 | 90-120 |
| Feed, f_z (mm/tooth) | 0.2-0.3 | 0.1-0.2 |
| Cutting depth, a_p (mm) | 2-4 | 1-2 |
| Tools according to ISO | coated cemented carbide K15, P25 | |

| SQUARE SHOULDER MILLING  | RADIAL DEPTH OF CUT, a_e | | |
|---|----------------------------------|----------------------|--------------------|
| | $a_e = 0.1 \times D$ | $a_e = 0.5 \times D$ | $a_e = 1 \times D$ |
| Cutting speed, v_c (m/min) | 120-140 | 100-120 | 80-110 |
| Feed, f_z (mm/tooth) | 0.25 | 0.15 | 0.10 |
| Tools according to ISO | coated cemented carbide K15, P25 | | |

Use a wear resistant coated cemented carbide e.g Coromant 3020 or Seco TP10.

| DRILLING  | | DRILL DIAMETER (mm) | | | | |
|--|------------------------------|---------------------|-----------|-----------|-----------|-----------|
| | | 1-5 | 5-10 | 10-20 | 20-30 | 30-40 |
| HSS | Cutting speed, v_c (m/min) | 5-10 | 5-10 | 5-10 | 5-10 | 5-10 |
| | Feed, f_z (mm/rev) | 0.05-0.15 | 0.15-0.25 | 0.25-0.35 | 0.35-0.40 | 0.40-0.45 |
| Coated HSS | Cutting speed, v_c (m/min) | 15-20 | 15-20 | 15-20 | 15-20 | 15-20 |
| | Feed, f_z (mm/rev) | 0.05-0.15 | 0.15-0.25 | 0.25-0.35 | 0.35-0.40 | 0.40-0.45 |
| Short hole drill indexable (cemented carbide) | Cutting speed, v_c (m/min) | - | - | - | 90-110 | 90-110 |
| | Feed, f_z (mm/rev) | - | - | - | 0.08-0.12 | 0.10-0.14 |
| Solid cemented carbide | Cutting speed, v_c (m/min) | - | - | 35 | 35 | 35 |
| | Feed, f_z (mm/rev) | - | - | 0.1-0.15 | 0.1-0.15 | 0.1-0.15 |
| Brazed cemented carbide | Cutting speed, v_c (m/min) | - | - | 30 | 30 | 30 |
| | Feed, f_z (mm/rev) | - | - | 0.1-0.2 | 0.1-0.2 | 0.1-0.2 |

TiCN or TiAlN multi layer are recommended coatings for HSS drilling.

MACHINING IN HARDENED CONDITION

ASP®2053 has been machined in hardened condition up to 65 HRC. CBN tools are recommended. Whisker reinforced ceramics (Coromant 670 or Kennametal 4300) can be used in turning, but the tool life is shorter and more difficult to predict.